

Vibrational properties of amorphous silicon from tight-binding $O(N)$ calculation

Parthapratim Biswas

*Debye Institute, Utrecht University, Princetonplein 5, 3508 TA Utrecht, The Netherlands**

We present an $O(N)$ algorithm to study the vibrational properties of amorphous silicon within the framework of tight-binding approach. The dynamical matrix elements have been evaluated numerically in the harmonic approximation exploiting the short-range nature of the density matrix to calculate the vibrational density of states which is then compared with the same obtained from a standard $O(N^4)$ algorithm. For the purpose of illustration, an 1000-atom model is studied to calculate the localization properties of the vibrational eigenstates using the participation numbers calculation.

PACS numbers: 71.55.Jv, 61.43.Dq, 63.50.+x

Keywords: amorphous silicon, $O(N)$ algorithm, vibrational modes

In recent years there has been a tremendous progress in the development of efficient $O(N)$ methods for electronic structure calculation of materials. There exist a number of $O(N)$ methods which have been developed to calculate the total energy of the systems and the electronic forces [1, 2, 3, 4, 5, 6]. Most of these algorithms utilize, in one way or another, the fact that the density matrix of the system to be studied is short-ranged [1, 5]. As a result, calculation of local electronic properties are possible by introducing a localization volume surrounding the region of interest where the local electronic properties are to be studied. The size of the localization volume depends on the decaying nature of the density matrix and for systems with a clean band gap, e.g., semi-conductors it has been observed that the density matrix decays exponentially [1, 4, 5]. Hence it is possible to define a localization volume having a linear dimension of the order of localization length of the density matrix. Although this does not appear to be trivially true in metallic systems [7], the *locality* in electronic structure calculation does indeed exist irrespective of the nature of the system and was first utilized by Friedel [8] who introduced the term *local density of states*. Later Heine [9] extended this idea of local electronic structure calculation of solids in real space in the context of Recursion method [9, 10] which has been further elaborated by Kohn [11] as the *principle of nearsightedness of equilibrium systems*.

In this paper we present an efficient algorithm for the calculation of vibrational properties of amorphous silicon from a tight-binding [12, 13] Hamiltonian exploiting the short-range nature of the density matrix. The motivation behind this work is the calculation of localization properties of the vibrational eigenstates of amorphous silicon. Recently, there has been a renewed interest in the study of the vibrational modes in disordered media [14, 15, 16]. These modes can be classified as either extended or localized depending on the energy of the state. In $d = 3$, the modes are expected to separate by sharp energy boundary, known as ‘mobility edge’ which marks the ‘localized

to delocalized’ transition. The corresponding analog in the electronic system is well-known after Anderson’s suggestion [17] that, unlike crystalline systems where electronic states are extended over the system, sufficient disorder can localize electronic states within the allowed energy bands. For vibrational eigenstates, however, the low frequency, long wavelength modes (sound) always exist. Garber et al. [16] studied an amorphous model of 4096 silicon atoms and demonstrated that at the mobility edge the vibrational eigenstates decay exponentially and localization length diverges as a power law above the edge. Although we are not going to address these issues here, the importance of the construction of dynamical matrix from tight-binding calculations and to study the nature of the vibrational states for a large, well-relaxed sample of amorphous silicon has its own merits.

In the following, we illustrate our work in two steps: first, we calculate the approximate electronic forces using an $O(N)$ algorithm starting from a tight-binding Hamiltonian. This is then followed by a calculation of harmonic normal modes of vibrations by direct diagonalization of the dynamical matrix. The diagonalization of a matrix is an expensive $O(N^3)$ operation, but since the time required to construct the dynamical matrix elements using this $O(N)$ approach is much larger compared to a single diagonalization for the system sizes to be considered here, we make no attempt to obtain the density of states using any $O(N)$ algorithm. In addition, we also study the nature of the vibrational eigenstates for which it is necessary to compute the eigenvectors of the dynamical matrix for participation numbers calculation. For the density of states calculation only, however, one can use any one of the $O(N)$ algorithms available in the literature which include Maximum Entropy approach by Drabold and Sankey [18], Recursion method of Haydock, Heine and Kelly [10] and Kernel Polynomial approximation by Silver and Roder [19, 20] etc. For our present purpose, a single diagonalization is easily affordable for the calculation of spectral quantities whereas the construction of a dynamical matrix using the exact electronic forces by direct diagonalization is extremely inefficient and time consuming which scales as $O(N^4)$ making it a formidable task to go beyond 500 atoms. This direct diagonalization

*Electronic address: P.Biswas@phys.uu.nl

approach is not practical and feasible for very large system size (≥ 10000 atoms). However, one can still obtain spectral density distribution using any one of the methods mentioned earlier and a few eigen vectors in appropriately chosen intervals using Lanczos algorithm in an $O(N)$ way to study the nature of the states.

Throughout this work, we have used the structural model generated by Barkema and Mousseau [21] as starting configurations which have been relaxed using the tight-binding Hamiltonian parameterized by Kwon et al. [22].

The general form of the tight-binding Hamiltonian H can be written as : $H = \sum_{i,L} \epsilon_{i,L} |i, L\rangle \langle i, L| + \sum_{i,L} \sum_{i',L'} V_{i,L;i',L'} |i, L\rangle \langle i', L'|$ and the corresponding total energy is $E = 2 \sum_k^{occup} \langle \Psi_k | H | \Psi_k \rangle + U_r + E_{at} N$. U_r stands for repulsive potential for the ion-ion interaction which can be represented either by a sum of pair potentials or as in the embedded atom model approach [23] as a functional of atomic density. N is the total number of atoms and E_{at} is a constant energy/atom. The electronic eigen function $|\Psi_k\rangle$ of H can be expanded as a linear combination : $|\Psi_k\rangle = \sum_{i,l} b_{i,l}^k |\phi_{l,i}\rangle$ of basis functions $\{|\phi_{l,i}\rangle\}$. For amorphous silicon, the minimal basis functions consist of one s -electron and three p -electrons per atom.

The dynamical matrix element between two atoms at sites i and j can be written as [24]

$$D_{i,\alpha}^{j,\beta} = \frac{1}{\sqrt{M_i M_j}} \left[\frac{F_n^{j,\beta} - F_o^{j,\beta}}{\Delta x_{i,\alpha}} \right] = \frac{1}{\sqrt{M_i M_j}} \left[\frac{\Delta F^{j,\beta}}{\Delta x_{i,\alpha}} \right],$$

where M_i, M_j are the atomic masses at the sites i and j respectively. $F_o^{j,\beta}, F_n^{j,\beta}$ are the forces acting on the atom at the site j in the $\beta (= x, y, z)$ direction due to displacement $\Delta x_{i,\alpha}$ of the atom at the site i in the α direction before and after the displacement respectively. A straight forward implementation [12, 13] of the above procedure for obtaining dynamical matrix elements between all the atoms require at least $(3N+1)$ direct diagonalizations for a system of N number of atoms. The total force acting on an atom (say i) can be written as,

$$\begin{aligned} F_i &= -\frac{\partial E}{\partial R_i} \\ &= -2 \frac{\partial}{\partial R_i} \sum_k^{occup} \langle \Psi_k | H | \Psi_k \rangle - \frac{\partial U_r}{\partial R_i} \end{aligned}$$

Using Hellman-Feynman theorem [25], the electronic part can be written as :

$$\begin{aligned} F_i^e &= -2 \frac{\partial}{\partial R_i} \sum_k \sum_{j,L} \sum_{j',L'} b_{j,L}^k b_{j',L'}^k \langle \phi_{j,L} | H | \phi_{j',L'} \rangle \\ &= -2 \sum_k \sum_{j,L} \sum_{j',L'} b_{j,L}^k b_{j',L'}^k \langle \phi_{j,L} | \frac{\partial H}{\partial R_i} | \phi_{j',L'} \rangle. \end{aligned}$$

The calculation of eigen vectors (b's) is an $O(N^3)$ operation and for the entire system (containing N atoms) the

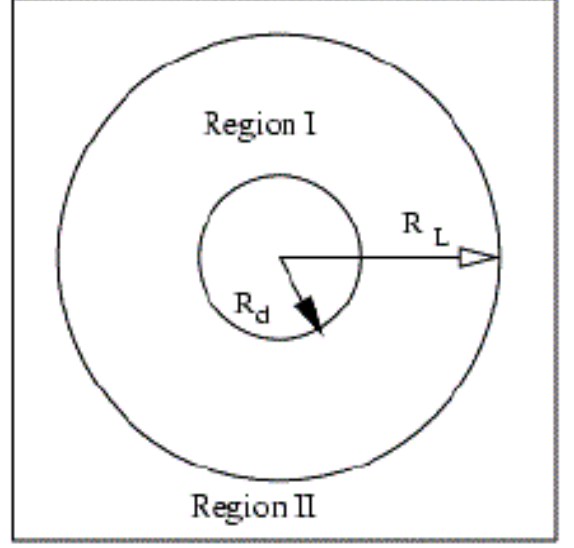


FIG. 1: Partitioning of the entire space for the calculation of dynamical matrix elements between the atom at the center of the sphere and those inside the small sphere of radius R_d . The large sphere with radius R_L corresponds to the localization volume (denoted by region I) for the atom at the center contributing to the forces on the atoms inside the small sphere.

scaling goes as $O(N^4)$. For each dynamical matrix element calculation one has to calculate the electronic force before and after the displacement of the atom and this has to be repeated for each direction $\beta (= x, y, z)$. For $N \geq 1000$, it is computationally overkill to construct the full dynamical matrix for the system. The calculation, however, can be performed in an $O(N)$ way by introducing a localization volume surrounding the atom on which the force is to be calculated as described below.

To calculate the electronic force using an $O(N)$ approach, we partition the entire system into regions I and II with the the atom as center as shown in figure 1. The large sphere with radius R_L corresponds to the localization volume for the central atom at i . The dynamical matrix elements between the atom i at the center and those inside the small sphere of radius R_d are to be constructed. Typically, R_d can be chosen as second neighbor distance of the central atom or more. By varying the radius R_d ($R_d < R_L$), one can monitor the magnitude of the dynamical matrix elements and can check whether they affect the vibrational density of states or not. The far away the atoms are from the central atom, the less is the effect of displacement on the atom at j [26].

One can, in fact, introduce a cut-off for dynamical matrix elements while storing the elements. Here we have used a value of $3.9\text{\AA}$ for R_d and $10\text{\AA}$ for R_L which we find is sufficient for the purpose of our calculation. The

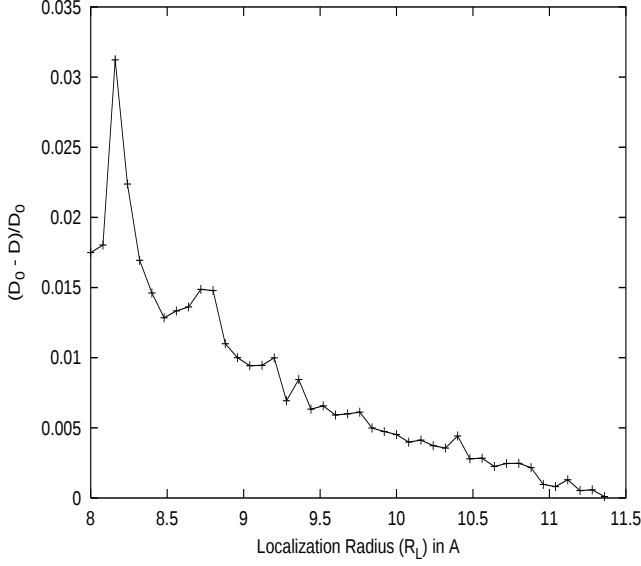


FIG. 2: The convergence behavior of dynamical matrix elements for different values of localization radius R_L . D and D_0 are the approximate and exact dynamical matrix elements respectively for each of the R_L values. For $R_L > 10\text{\AA}$, the error is observed to be less than 1 percent.

difference of force on an atom j due to the displacement of the atom i at the center can be written as :

$$\begin{aligned}\Delta F^j &= [F_{n,I}^j + F_{n,II}^j] - [F_{o,I}^j + F_{o,II}^j] \\ &= [F_{n,I}^j - F_{o,I}^j] + [F_{n,II}^j - F_{o,II}^j] \\ \Delta \tilde{F}^j &\approx [F_{n,I}^j - F_{o,I}^j]\end{aligned}$$

where $F_{o,I}^j$ ($F_{o,II}^j$) and $F_{n,I}^j$ ($F_{n,II}^j$) are the contribution to the total forces from the region I (region II) on the atom j before and after the displacement of the atom i at the center respectively. ΔF^j and $\Delta \tilde{F}^j$ are the exact and approximate difference of total forces at the atom j . Our $O(N)$ algorithm is based on the assertion that the approximate difference of total force can be obtained by neglecting the contribution from region II if the radius of the region I is greater than the localization length of the density matrix. This assertion can be verified simply by looking at the convergence behavior of the dynamical matrix elements with respect to the radius of the localization volume. The approximate difference of force can now be written as a sum of electronic and repulsive contribution :

$$\begin{aligned}\Delta \tilde{F}^j &= \Delta \tilde{F}^{j,e} + \Delta \tilde{F}^{j,r} \\ \Delta \tilde{F}^{j,e} &= (F_{n,I}^{j,e} - F_{o,I}^{j,e})\end{aligned}$$

with

$$F_{x,I}^{j,e} = -2 \sum_k \sum_{jL,j'L'} (b_{jL}^{k,I})^x (b_{j'L'}^{k,I})^x \langle \phi_{jL} | \frac{\partial H_I^x}{\partial R_i} | \phi_{j'L'} \rangle$$

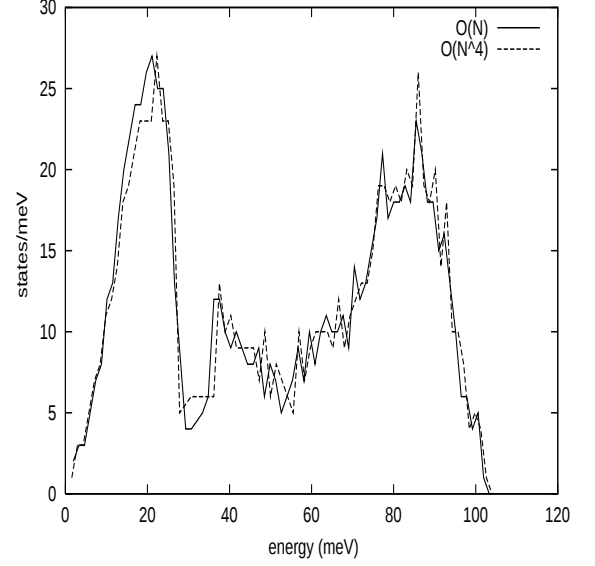


FIG. 3: The density of vibrational states for a system of 500-atom model calculated using the $O(N)$ force algorithm described in the text. The same from a standard $O(N^4)$ force calculation is also plotted (denoted by a dotted line) for comparison.

where H_I^x is the Hamiltonian of the region I before ($x = o$) and after the displacement ($x = n$) of the atom at the center.

We have observed that a localization volume of radius $10\text{\AA}$, typically containing 200 to 225 atoms, gives a very good estimate of $\Delta \tilde{F}^j$ for calculation of dynamical matrix elements. If we neglect contributions from region II, the force calculation on a single atom is an $O(1)$ operation as the size of region I is independent of the total system size and the full dynamical matrix construction is an $O(N)$ operation for N atoms. Since the dimension of the truncated Hamiltonian matrices H^I are much smaller than the Hamiltonian matrix H of the total system, the electronic forces can be calculated by direct diagonalization of the truncated Hamiltonian matrix H_I which is also independent of the system size. In practice, the accuracy of $\Delta \tilde{F}^j$ depends on two factors – the step size of displacement and the volume of region I which is again related with the size of band-gap. The accuracy can be improved in a controlled manner by (a) choosing a small displacement which is a necessary condition for the harmonic approximation to be valid and, (b) increasing the radius of the localization volume. We would like to mention that a similar but not identical approach based on the use of localized Wannier-like functions and truncating the dynamical matrix beyond a cutoff was reported by Ordejon et al. [27].

In figure 2 we have presented convergence behavior of dynamical matrix elements with respect to different localization radius R_L . The estimate of approximate electronic forces and hence the dynamical matrix elements are found to be very good and the percentage error is

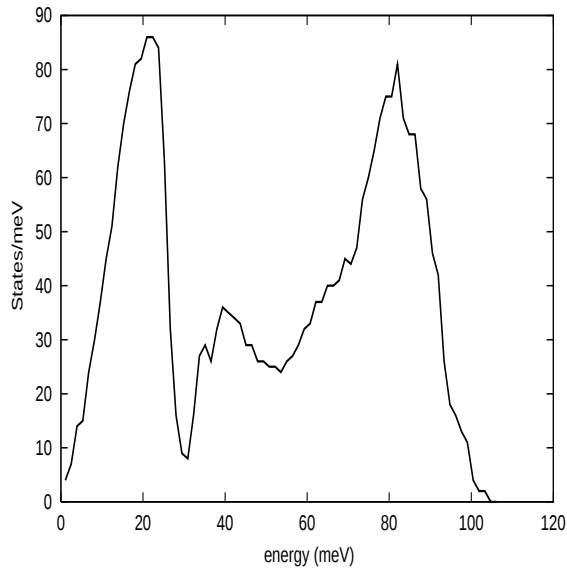


FIG. 4: The vibrational density of states for a system of 1000-atom obtained using the $O(N)$ force algorithm described in the text.

observed to be as low as 0.5 for $R_L \geq 10\text{\AA}$. The results of our calculations are presented in the figure 3 where we have plotted the density of vibrational states obtained from a 500-atom model. For the purpose of comparison, we have also plotted the density of states using the full Hamiltonian matrix by a standard $O(N^4)$ algorithm. It is quite clear from the figure 3 that the quality of (electronic) forces obtained from the $O(N)$ algorithm is very good giving the same vibrational density of states as one would expect using the full Hamiltonian matrix. We should mention that to generate the dynamical matrix elements for this 500-atom model using standard $O(N^4)$ force algorithm took 80 hours in contrast to 13.5 hours using the $O(N)$ algorithm in a DEC alpha (667 MHz) workstation.

Having established that the dynamical matrix obtained in this $O(N)$ way is sufficiently accurate, we now study the nature of the vibrational states for a model of 1000-atom. The configuration is first relaxed using the tight-binding Monte Carlo calculation as outlined in the Ref. [28]. The vibrational density of states of the Monte Carlo relaxed structure is shown in the figure 4 which has been obtained by direct diagonalization of the dynamical matrix. Since the dynamical matrix construction for this 1000-atom model took approximately 27 hours, we therefore avoid to use any one of the $O(N)$ algorithm mentioned in the Refs. [18, 19, 20] for the calculation of vibrational density of states (VDOS). The VDOS in figure 4 clearly shows two peaks : a low energy acoustical peak at 20 meV and a high energy optical peak at 80 meV. The ratio of the height of two peaks are of the same order as observed in the experimental data obtained by Kamitakahara et al. [29]. The optical peak is, however, at higher energy compared to the experimental value and

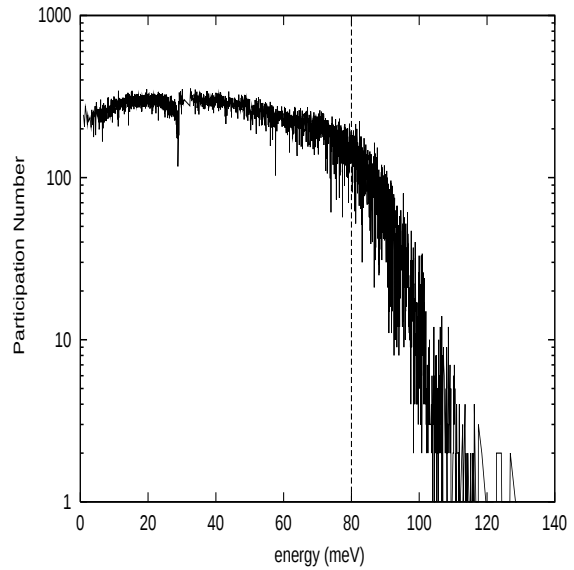


FIG. 5: The participation numbers (in log scale) for a model of 1000-atom with energy. The number drops near around 80 meV showing the localized character of the eigenstates which is marked by a vertical line.

the value obtained from empirical potential calculations. Such a high energy optical peak has been also observed in the calculation of Klein et al. [30] who studied hydrogenated amorphous silicon using tight-binding molecular dynamics. We believe that this discrepancy in the position of the high energy optical peak is associated with the repulsive part of the potential used in this calculation. The potential produces the correct electronic density of states within the accuracy of a fraction of an eV; however, for the vibrational density of states calculation an accuracy of the order of few meVs is required to produce the peaks at right positions.

In order to get an idea about the nature of the vibrational states, we need to calculate the participation numbers from the eigenvectors of the dynamical matrix. Since the eigenvectors calculation is a memory as well as CPU intensive operation, it is not a very suitable tool for dealing with very large system sizes. We therefore restrict ourselves to an 1000-atom model for this purpose. The participation numbers give a measure of the degree of localization of the wave functions to be studied. Let ϕ_j denotes the amplitude of the j -th normalized eigenvector. A simple measure of the number of sites participated in contributing the eigenstate gives the participation number $P_N(j)$ and is defined as $P_N^{-1}(j) = \sum_i |\phi_j(i)|^4$. A complete localized state therefore corresponds to $P_N = 1$, whereas for an extended state $P_N = N$. In figure 5, we have plotted the participation numbers with energy in meV. In the low energy region the value of the participation number fluctuates around 300. The drop of the participation numbers around 80 meV is actually somewhat higher than that was observed in the work of Allen et al. [14] who found a value of around 70 meV. This differ-

ence is, however, consistent with what we have observed in figure 4 where the optical peak appears at somewhat higher energy. In spite of this difference, we find that the general trend of the participation numbers with energy (meV) follows the same course as was observed in Ref. [14]. For example, a small dip at 30 meV in the figure 5 has been also observed in Ref. [14]. A closer inspection of the localization properties using the participation numbers requires a much larger system size to be studied for better statistics, particularly, in the high energy region where a delocalized - localized transition is expected to occur from the low energy side. The tight-binding calculation for a model of 10 000-atom is in progress and in a future communication we will address the energy-level-spacing distribution and eigen function statistics of the spectrum.

In conclusion, we have presented an $O(N)$ algorithm for the calculation electronic force for amorphous semiconductors from tight-binding Hamiltonian exploiting the short-range nature of the density matrix. This algorithm has been used to construct the dynamical matrix

for a 500-atom model of amorphous silicon. The vibrational density of states calculated from this $O(N)$ dynamical matrix has been observed to be in excellent agreement with the same obtained from a standard $O(N^4)$ algorithm. Furthermore, we have used this algorithm to study the nature of the vibrational states for a model of 1000-atom amorphous silicon, the dynamical matrix of which is otherwise difficult to construct in the tight-binding approach. The participation numbers calculation suggests that the results of this tight-binding calculation are in agreement with the results based on empirical model potentials.

The author acknowledges G. T. Barkema of Institute for Theoretical Physics, Utrecht University for providing the coordinates of amorphous silicon samples which have been used as starting configurations in the present calculations. The author also thanks David Drabold of Ohio University for a careful reading of the revised manuscript. The work has been supported by NWO within the priority program "Solar Cells in the 21st Century".

-
- [1] S. Goedecker, Reviews of Mod. Phys. **71**, 1085 (1999) and references therein.
 - [2] P.Ordejon, D.A. Drabold, R.M. Martin and, M.P. Grumbach, Phys. Rev. B **51**, 1456 (1995)
 - [3] X.-P. Li, R.W Nunes and D. Vanderbilt, Phys. Rev. B **47**, 10891 (1993); R.W. Nunes and D. Vanderbilt, Phys. Rev. B **50**, 17611 (1994)
 - [4] U. Stephan and D.A. Drabold, Phys. Rev. B **57**, 6391 (1998)
 - [5] R. Baer and M. Head-Gordon, Phys. Rev. Lett. **79**, 3962 (1997)
 - [6] D. R. Bowler and M. J. Gillan, Comp. Phys. Comm. **120**, 95 (1999)
 - [7] The density matrix of a metallic system at zero temperature decays algebraically. However, at finite but low temperature this behavior changes to an exponentially decay modulated by the cosine terms. For details see, S. Goedecker and O. Ivanov, Sol. State Comm., **105** 665 (1998a); S. Ismail-Beigi and T. Arias, Phys. Rev. B **57**, 11923 (1998)
 - [8] J. Friedel, Adv. Phys. **3**, 446 (1954)
 - [9] V. Heine in *Solid State Physics* (Vol. 35, edited by H. Ehrenreich, F. Seitz and D. Turnbull, Academic Press, 1980).
 - [10] R. Haydock in *Solid state Physics* (Vol. 35, edited by H. Ehrenreich, F. Seitz and D. Turnbull, Academic Press, 1980);
 - [11] W. Kohn, Phys. Rev. Lett. **76**, 3168 (1996).
 - [12] L. Colombo, Annual Reviews of Computational Physics, Vol. 4, Pg. 147 (edited by D. Stauffer, World Scientific, Singapore, 1996)
 - [13] C.M.Goringe, D.R.Bowler and E.H.Hernandez, Rep. Prog. Phys. **60**, 1447 (1997)
 - [14] P. B Allen, J. L Feldman, J. Fabian and, F. Wooten, Phil. Mag. Lett. **81**, 433 (2001)
 - [15] S. N. Taraskin and S. R. Elliot, J.Phys.: Condens. Matter **11**, A219 (1999)
 - [16] W. Garber, F. M. Tangerman, P.B. Allen, and J. L Feldman, cond-mat/0101070
 - [17] P. Anderson, Phys. Rev. **109**, 1492 (1958)
 - [18] D. A. Drabold and O. F. Sankey, Phys. Rev. Lett. **70**, 3631 (1993)
 - [19] A. F. Voter, J. D. Kress, and R. N. Silver, Phys. Rev. B **53**, 12733 (1996)
 - [20] R. N. Silver and H. Roder, Phys. Rev. E **56**, 4822 (1997)
 - [21] G.T. Barkema and N. Mousseau, Phys. Rev. B **62**, 4985 (2000).
 - [22] I. Kwon, R. Biswas, C. Z Wang, K. M Ho and C. M Soukoulis, Phys. Rev. B **49**, 7242 (1994).
 - [23] M. W. Daw and M. I. Baskes. Phys. Rev. B **29**, 6443 (1984)
 - [24] D.A Drabold, NATO Advanced Study Institute Series, (edited by M. F. Thorpe and M. I Mitkova, Kluwer, Dordrecht, 1997)
 - [25] R. P. Feynman, Phys. Rev. **56**, 340 (1939).
 - [26] This is not entirely true in presence of a long-range interaction when the locality principle can not be applied trivially. In this respect, our method can not be applied to systems where the long-range contribution to electronic force is significant.
 - [27] P Ordejon, David A Drabold, Richard M. Martin, and Satoshi Itoh, Phys. Rev. Lett. **75**, 1324 (1995)
 - [28] P. Biswas, G. T. Barkema, N. Mousseau and, W. F. Van der Weg, Europhys. Lett. **56**, 427 (2001)
 - [29] W. A. Kamitakahara, C. M Soukoulis, H. R Shanks and, U. Buchenau, Phys. Rev. B **36** 6539 (1987)
 - [30] P. Klein, H. M. Urbassek and, T. Frauenheim, Phys. Rev. B **60**, 5478 (1999)